



# TEST REPORT

1. NO : CT23-092057E
2. Client
  - Name : SSANGKOM CO., LTD.
  - Address : 61, Gwangnaman-ro, Gwangju-si, Gyeonggi-do, Korea
3. Date of Test : 2023.10.17 ~ 2023.12.26
4. Use of Report : Quality control
5. Test Sample : PERFECT FLEX(ISO 13007 C2S1TE)
6. Test Method
  - (1) KS L ISO 13007-2:2013



Affirmation	Tested By	Technical Manager
	Name : Noh sang kyun <i>Noh Sang</i>	Name : Lee, Bong Chun <i>Lee</i>

This report is not accredited by KOLAS and KS Q ISO/IEC 17025.  
 Our report apply only to the standards or procedures identified and to the sample(s) tested unless otherwise specified. The test results are not indicative of representative of the qualities of the lot from which the sample was taken or of apparently identical or similar products. The results of using only a portion of this report cannot be guaranteed. The authenticity of this test report can be checked on KCL website([www.kcl.re.kr](http://www.kcl.re.kr)).

2023. 12. 26

Korea Conformity Laboratories President Jo, Yung Tae *Jo Yung Tae*

Result Inquiry : 73, Yangcheong 3-gil, Ochang-eup, Cheongwon-Gu, Cheongju-Si, Chungbuk, Korea (82-43-210-8955)

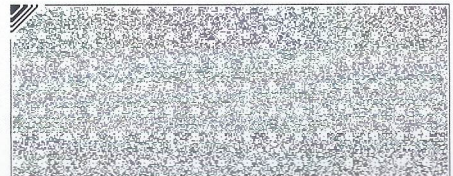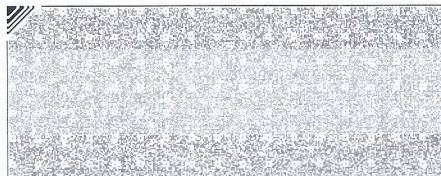

# TEST REPORT

No : CT23-092057E

## 7. Test Results

1) PERFECT FLEX(ISO 13007 C2SITE)

Test Item(s)	Unit	Test Method	Test Results	Remark	Loc.
Tensile adhesion strength	N/mm <sup>2</sup>	(1)	1.8(CF-A)	(23±2) °C. (50±5) % R.H.	A
Tensile adhesion strength after water immersion	N/mm <sup>2</sup>	(1)	1.2(CF-A)		
Tensile adhesion strength after heat aging	N/mm <sup>2</sup>	(1)	1.9(CF-A)		
Tensile adhesion strength after freeze-thaw cycle	N/mm <sup>2</sup>	(1)	1.1(CF-A)		
Open time : Tensile adhesion strength(After 30 min)	N/mm <sup>2</sup>	(1)	1.4(CF-A)		
Slip	mm	(1)	0.1		
Transverse deformation	mm	(1)	3.6		

※ Mix proportion(Mass ratio)

Sample : Water = 100 : 27

※ Location

A : 73, Yangcheong 3-gil, Ochang-eup, Cheongwon-Gu, Cheongju-Si, Chungbuk, Korea

----- End of Report -----

